



Standard Test Method for Determining the Integrity of Nonreinforced Geomembrane Seams Produced Using Thermo-Fusion Methods¹

This standard is issued under the fixed designation D 6392; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method describes destructive quality control and quality assurance tests used to determine the integrity of geomembrane seams produced by thermo-fusion methods. This test method presents the procedures used for determining the quality of nonbituminous bonded seams subjected to both peel and shear tests. These test procedures are intended for nonreinforced geomembranes only.

1.2 The types of thermal field seaming techniques used to construct geomembrane seams include the following.

1.2.1 *Hot Air*—This technique introduces high-temperature air or gas between two geomembrane surfaces to facilitate melting. Pressure is applied to the top or bottom geomembrane, forcing together the two surfaces to form a continuous bond.

1.2.2 *Hot Wedge (or Knife)*—This technique melts the two geomembrane surfaces to be seamed by running a hot metal wedge between them. Pressure is applied to the top or bottom geomembrane, or both, to form a continuous bond. Some seams of this kind are made with dual bond tracks separated by a nonbonded gap. These seams are sometimes referred to as dual hot wedge seams or double-track seams.

1.2.3 *Extrusion*—This technique encompasses extruding molten resin between two geomembranes or at the edge of two overlapped geomembranes to effect a continuous bond.

1.3 The types of materials covered by this test method include the following.

1.3.1 *Very Low Density Polyethylene (VLDPE)*.

1.3.2 *Linear Low Density Polyethylene (LLDPE)*.

1.3.3 *Very Flexible Polyethylene (VFPE)*.

1.3.4 *Linear Medium Density Polyethylene (LMDPE)*.

1.3.5 *High Density Polyethylene (HDPE)*.

1.3.6 *Polyvinyl Chloride (PVC)*.

1.3.7 *Flexible Polypropylene (fPP)*.

Note 1—The polyethylene identifiers presented in 1.3.1–1.3.5 describe the types of materials typically tested using this test method. These are industry accepted trade descriptions and are not technical material classifications based upon material density.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:²

D 638 Test Method for Tensile Properties of Plastics

D 882 Test Method for Tensile Properties of Thin Plastic Sheeting

D 4439 Terminology for Geosynthetics

D 5199 Test Method for Measuring the Nominal Thickness of Geosynthetics

D 5994 Test Method for Measuring Core Thickness of Textured Geomembrane

2.2 EPA Standards:

EPA/600/2-88/052 Lining of Waste Containment and Other Containment Facilities; Appendix N, Locus of break codes for various types of FML seams³

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *geomembrane, n*—essentially impermeable geosynthetic composed of one or more synthetic sheets.

3.1.2 *quality assurance, n*—all planned and systematic actions necessary to provide adequate confidence that an item or a facility will perform satisfactorily in service.

3.1.3 *quality control, n*—the operational techniques and the activities, which sustain a quality of material, product, system, or service that will satisfy given needs; also the use of such techniques and activities.

4. Significance and Use

4.1 The use of geomembranes as barrier materials to restrict liquid migration from one location to another in soil and rock has created a need for a standard test method to evaluate the

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from the Superintendent of Documents, US Government Printing Office, Washington, DC 20402.

This test method is under the jurisdiction of ASTM Committee D35 on Geosynthetics and is the direct responsibility of Subcommittee D35.10 on Geomembranes.

Current edition approved Jan. 1, 2006. Published June 2006. Originally approved in 1999. Last previous edition approved in 1999 as D 6392–99.

quality of geomembrane seams produced by thermo-fusion methods. In the case of geomembranes, it has become evident that geomembrane seams can exhibit separation in the field under certain conditions. Although this is an index type test method used for quality assurance and quality control purposes, it is also intended to provide the quality assurance engineer with sufficient seam peel and shear data to evaluate seam quality. Recording and reporting data, such as separation that occurs during the peel test and elongation during the shear test, will allow the quality assurance engineer to take measures necessary to ensure the repair of inferior seams during facility construction, and therefore, minimize the potential for seam separation in service.

5. Apparatus

5.1 Tensile instrumentation shall meet the requirements outlined in Test Method D 638.

5.2 *Grip Faces*—Grip faces shall be 25 mm (1 in.) wide and a minimum of 25 mm (1 in.) in length. Smooth rubber, fine serrated or coarse serrated grip faces have all been found to be suitable for testing geomembrane seams.

6. Sample and Specimen Preparation

6.1 *Seam Samples*—Cut a portion of the fabricated seam sample from the installed liner in accordance with the project specifications. It is recommended that the cutout sample be 0.3 m (1 ft) wide and 0.45 m (1.5 ft) in length with the seam centered in the middle.

6.2 *Specimen Preparation*—Ten specimens shall be cut from the sample submittal. The specimens shall be die cut using a 25 mm (nominal 1 in.) wide by a minimum of 150 mm (nominal 6 in.) long die. Specimens that will be subjected to peel and shear tests shall be selected alternately from the sample and labeled as shown in Fig. 1. Specimens shall be cut such that the seam is perpendicular to the longer dimension of the strip specimen.

6.3 *Conditioning*—Samples should be conditioned for 40 h in a standard laboratory environment that conforms to the

requirements for testing geosynthetics as stated in Terminology D 4439. Long sample conditioning times typically are not possible for most applications that require seam testing. Prior to testing, samples should be conditioned for a minimum of 1 h at $23 \pm 2^\circ\text{C}$ and a relative humidity between 50 and 70 %.

7. Destructive Test Methods

7.1 *Peel Testing*—Subject five specimens to the 90° "T-Peel" test (see Fig. 2). If the tested sample is a dual hot wedge seam, five specimens must be examined for each external track of the seam. Maintaining the specimen in a horizontal position throughout the test is not required. Fully grip the test specimen across the width of the specimen. Grip the peel specimen by securing grips 25 mm (1 in.) on each side of the start of the seam bond, a constant machine cross head speed of 50 mm (2 in.)/min for HDPE, LMDPE, and PVC, 500 mm (20 in.)/min for LLDPE, VLDPE, VFPE, and fPP. The test is complete when the specimen ruptures.

7.2 *Shear Testing*—Subject five specimens to the shear test (see Fig. 2). Fully support the test specimen within the grips across the width of the specimen. Secure the grips 25 mm (1 in.) on each side of the start of the seam bond, a constant machine cross head speed of 50 mm (2 in.)/min for LMDPE and HDPE, 500 mm (20 in.)/min for fPP, LLDPE, VFPE, VLDPE, and PVC. The test is complete for HDPE and LMDPE once the specimen has elongated 50 %. PVC, fPP, LLDPE, VFPE and VLDPE geomembranes should be tested to rupture.

NOTE 2—Both peel and shear tests for fPP, LLDPE, VLDPE, and PVC geomembranes have been tested routinely at both 2 and 20 in./min. When conducting seam peel or shear testing for quality control, or quality assurance purposes, or both, it may be necessary to select the manufacturer's recommended testing speed. In the absence of explicit testing speed requirements, follow those recommended in 7.1 and 7.2.

8. Calculations and Observations

8.1 *Estimate of Seam Peel Separation*—Visually estimate the seam separation demonstrated prior to rupture for peel specimens. The estimate shall be based upon the proportion of

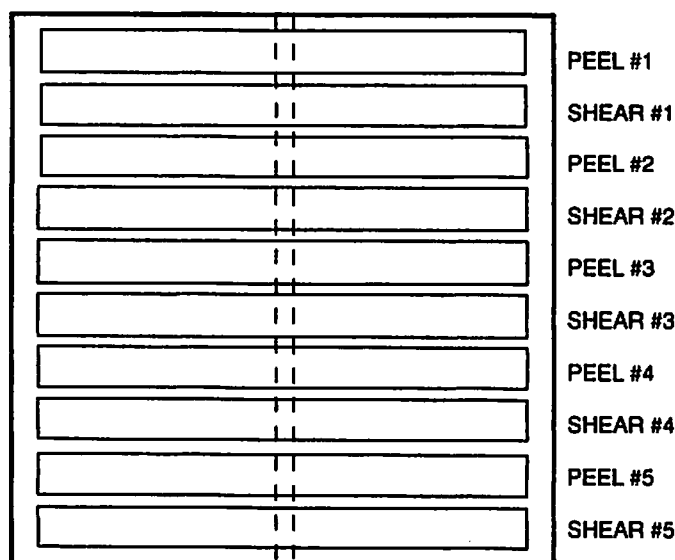


FIG. 1 Seam Sample

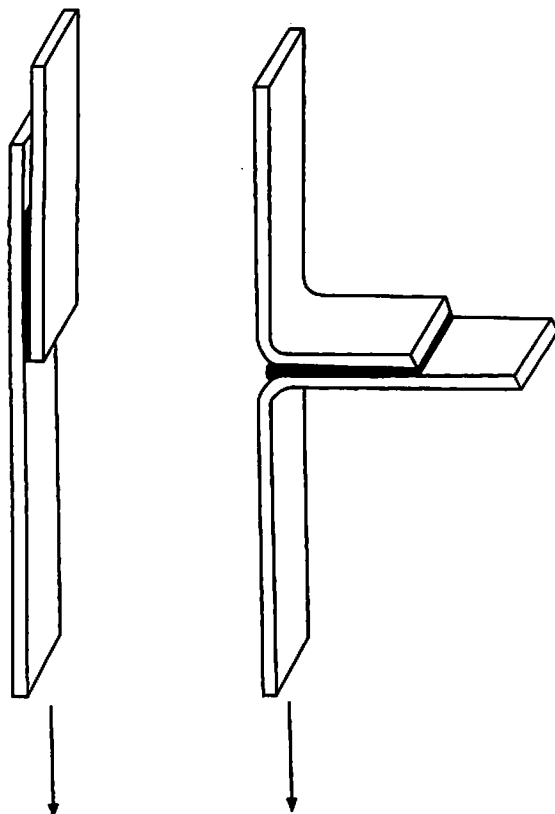


FIG. 2 Shear and T-Peel Specimens

ear length of separated bond in the direction of the test, to
length of original bonding to the nearest 25 %.

NOTE 3—During the thermo-fusion welding process, some of the
melted polymer may be shifted to the outside of the weld during the
pressing of the geomembrane panels together. This melted polymer is
sometimes called “squeeze-out” or “bleed out” and is not considered part
of the bond. Care must be exercised during estimation of the seam peel
separation to segregate the squeeze or bleed out length from the peeled
bond length. The reported peel separation shall include the peeled bond
length only.

8.2 *Rupture Mode Selection*—Determine the locus of break
for both the peel and shear specimens as shown in Figs. 3 and 4.
The locus of break for shear specimens that do not rupture
prior to test end (50 % elongation) shall be interpreted as
occurring in the membrane that exhibits yielding.

8.3 *Shear Percent Elongation*—Calculate the percent elongation
on shear specimens according to Eq 1. Divide the
tension at test end by the original gage length of 25 mm and
multiply by 100.

$$\text{Elongation} = E \frac{L}{L_0} \times 100 \quad (1)$$

where:

- E = extension at test end, and
- L = original gage length.

NOTE 4—The intent of measuring elongation using this test method is
to identify relatively large reductions in typical break elongation values of
geomembrane samples. Length is defined as the distance from one grip to the seam
center. Using this definition implies that all strain experienced by the

specimen during the shear test occurs on one side of the seam. Of course
this assumption is inaccurate, since some strain will occur on each side of
the seam, and in the seam area itself; however, it is difficult to make an
accurate measurement of the strain distribution which occurs in the
specimen during testing. Further, it is not critical to know the exact
location of all the strain which occurs during testing but rather to simply
identify when significant reductions in elongation (when compared with
the typical elongation of a new material) have occurred.

9. Report

9.1 The report shall include the following information.

9.1.1 Report the individual peel and shear specimen maximum
unit tension values in N/mm of width (lb/in.).

NOTE 5—If requested, report the maximum peel or shear stress. This
calculation will require an accurate measurement of thickness for each
specimen. These measurements should be made in accordance with Test
Method D 5199 for smooth geomembranes and Test Method D 5994 for
textured geomembranes.

9.1.2 Report the cross head speed used during peel and
shear testing.

9.1.3 Report the average of the individual peel and shear
sample values recorded.

9.1.4 If the peel or shear specimen does not rupture, report
the elongation at the maximum cross-head travel limitation. If
the gage length is reduced to less than 25 mm (1 in.), this must
be noted in the report.

9.1.5 Report the mode of specimen rupture for peel and
shear specimens according to Fig. 3 or Fig. 4.

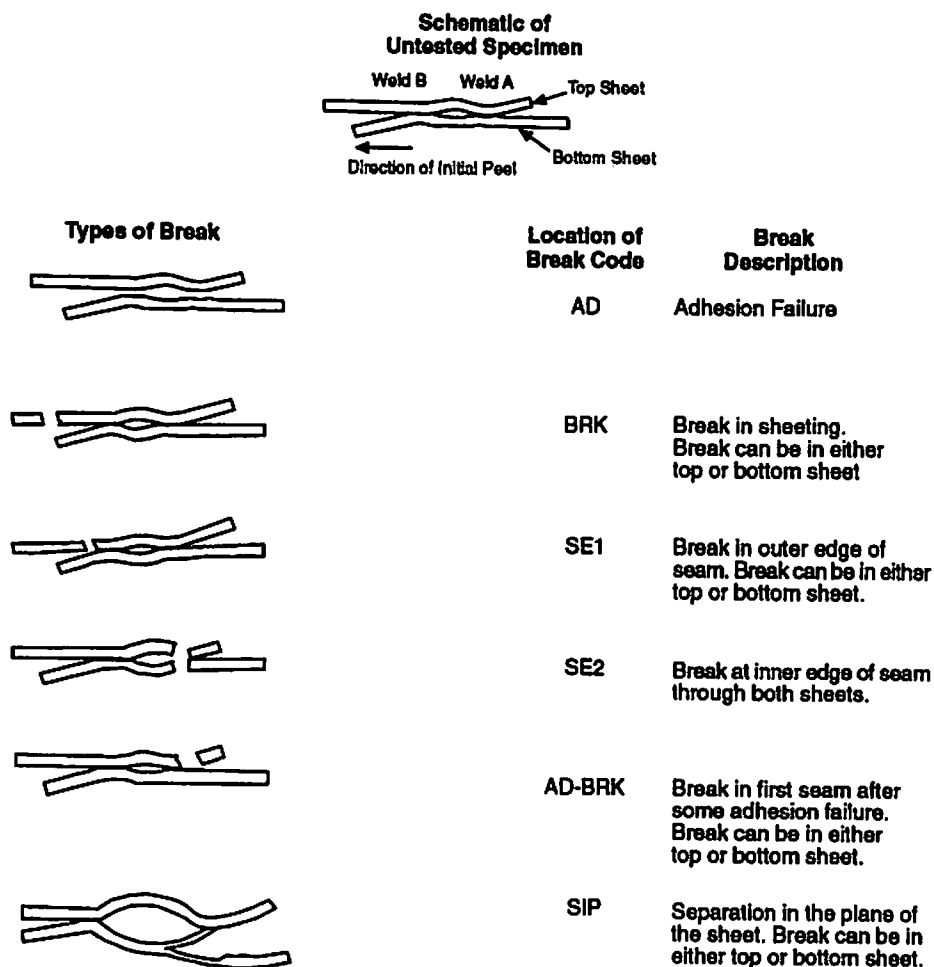



FIG. 3 Locus-of-Break Codes for Dual Hot Wedge Seams in Unreinforced Geomembranes Tested for Seam Strength in Shear and Peel Modes

NOTE 6—"Locus-of-Failure" (Figs. 3 and 4) include only some of the typically found seam configurations found in the industry. When this test method is applied to seams bonded in configurations other than those identified in Fig. 3 or Fig. 4, the users of this test method must agree on applicable descriptions for modes of specimen rupture.


10. Precision and Bias

10.1 No statement can be made at this time concerning precision or bias.

**Schematic of
Untested Specimen**



Types of Break

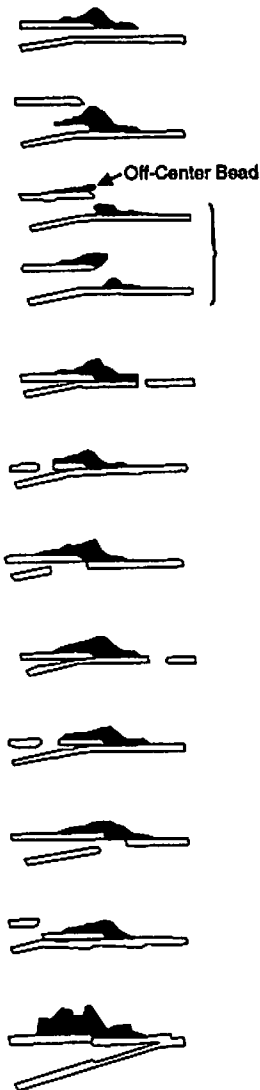

**Location of
Break Code**

Break Description

AD1

Failure in adhesion. Specimens may also delaminate under the bead and break through the thin extruded material in the outer area.

AD2

Failure in adhesion.

AD-WLD⁽¹⁾

Break through the fillet.

SE1

Break at seam edge in the bottom sheet (applicable to shear only).

SE2

Break at seam edge in the top sheet (applicable to shear only).

SE3

Break at seam edge in the bottom sheet (applicable to peel only).

BRK1

Break in the bottom sheeting. A "B" in parentheses following the code means the specimen broke in the buffed area.

BRK2

Break in the top sheeting. A "B" in parentheses following the code means the specimen broke in the buffed area.

AD-BRK

Break in the bottom sheeting after some adhesion failure between the fillet and the bottom sheet.

HT

Break at the edge of the hot tack for specimens which could not be delaminated in the hot tack.

SIP

Separation in the plane of the sheet.

(1) Acceptance of AD-WLD breaks may depend on whether test values meet a minimum specification value.

FIG. 4 Locus-of-Break Codes for Fillet Extrusion Weld Seams in Unreinforced Geomembranes Tested for Seam Strength in Shear and Peel Modes

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).

1. S

1.

appr

in g

repo

1.

flexi

reinf

reinf

1.

the s

ible

1.

safet

respu

prial

bility

2. R

2.

D

1

D

1

D

D

1

D

D

1

1

D

1

D

D

1

and is

Cut

in 199

2 P

contad

Standd

the AS

Copyr