

Decorative high-pressure laminates (HPL) — Sheets based on thermosetting resins

Part 1. Specifications

This European Standard EN 438-1 : 1991 has the status of a
British Standard

Stratifiés décoratifs haute pression (HPL) -
Plaques à base de résins thermodurcissables -
Partie 1: Spécifications

Dekorative Hochdruck -
Schichtpreßstoffplatten (HPL) - Platten auf
Basis härtpbarer Harze -
Teil 1: Spezifikation

NO COPYING IN ANY FORM WITHOUT WRITTEN PERMISSION FROM BSI



Cooperating organizations

The European Committee for Standardization, under whose supervision this European Standard was prepared, comprises the national standards organizations of the following Western European countries.

Austria	Oesterreichisches Normungsinstitut
Belgium	Institut belge de normalisation
Denmark	Dansk Standardiseringsraad
Finland	Suomen Standardisoimislito, r.y.
France	Association française de normalisation
Germany	Deutsches Institut für Normung e. V.
Greece	Hellenic Organization for Standardization
Iceland	Technological Institute of Iceland
Ireland	National Standards Authority of Ireland
Italy	Ente Nazionale Italiano di Unificazione
Luxembourg	Inspection du Travail et des Mines
Netherlands	Nederlands Normalisatie-instituut
Norway	Norges Standardiseringsforbund
Portugal	Instituto Português da Qualidade
Spain	Asociación Española de Normalización y Certificación
Sweden	Standardiseringskommissionen i Sverige
Switzerland	Association suisse de normalisation
United Kingdom	British Standards Institution

This British Standard was published under the authority of the Standards Board and comes into effect on 31 October 1991

© BSI 1991

The following BSI references relate to the work on this standard:
Committee reference PRM/76
Draft 88/35026

ISBN 0 580 19900 2

Amendments issued since publication

Amd. No.	Date	Text affected

Contents

	Page
Cooperating organizations	Inside front cover
National foreword	i
Foreword	2
Text of EN 438-1 : 1991	3
Specification	
0 Introduction	3
1 Scope and field of application	3
2 Reference	3
3 Definition	3
4 Classification	3
5 Requirements	5
6 Properties	6
Annexes	
A Addendum to specification table 7, relating to test methods 7,9 and 10	10
B Addendum to specification table 7, relating to test method 14	13
Tables	
1 Classification system and typical applications	4
2 Index for resistance to surface wear	5
3 Index for resistance to impact	5
4 Index for resistance to scratching	5
5 Permitted variations of thickness	6
6 Permitted departure from flatness	7
7 Property requirements	8
Figures	
1 Broken corner	6
2 Measurement of straightness	7
3 Measurement of squareness	7
4 Effects of surface finish and colour on scratch resistance	13
National appendices	
National appendix NA	Inside back cover
National appendix NB	Inside back cover

National foreword

This British Standard has been prepared under the direction of the Plastics and Rubber Standards Policy Committee and is the English language version of EN 438-1 'Decorative high-pressure laminates (HPL) — Sheets based on thermosetting resins — Part 1 : Specifications', published by the European Committee for Standardization (CEN). This Part of BS EN 438 supersedes BS 3794 : Part 1 : 1986 which is withdrawn. EN 438-1 was produced as a result of international discussions in which the United Kingdom took an active part.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 438-1 : 1991

May 1991

UDC 674.1.03:674.812.2-41

Descriptors: Plastics, laminated plastics, decorative coatings, thermosetting resins, plates, classifications, specifications

English version

Decorative high-pressure laminates (HPL) — Sheets
based on thermosetting resins — Part 1:
Specifications

(ISO 4586-1 : 1987 modified)

Stratifiés décoratifs haute pression (HPL) —
Plaques à base de résins thermodurcissables
— Partie 1:
Spécifications (ISO 4586-1 : 1987 modifiée)

Dekorative Hochdruck —
Schichtpreßstoffplatten (HPL) —
Platten auf Basis härtpbarer Harze —
Teil 1: Spezifikation (ISO 4586-1 : 1987
modifiziert)

This European Standard was approved by CEN on 24 October 1990. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

© CEN 1991 Copyright reserved to all CEN members

Ref. No. EN 438-1 : 1991 E

Foreword

This European Standard has been drawn up by a CEN ad hoc group for decorative laminates. It has been prepared as a result of the primary questionnaire procedure (PQ) based on ISO 4586-1 : 1987.

The principal modifications compared with the International Standard are the definition for sheets of decorative high pressure laminates (HPL) and the introduction of a correlation table between the two systems of alphabetical and numerical classification of decorative high pressure laminates.

The Secretariat of the ad hoc group on decorative laminates is held by AFNOR.

According to the Common CEN/CENELEC Rules, the following countries are bound to implement this European Standard:

Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

0 Introduction

The first part of this standard includes requirements for the types of materials that are classified in clause 4.

The requirements for several properties may be satisfied by alternative test methods. These have been included where the requirements by either method are approximately equivalent, and either where expensive equipment of different types is in satisfactory use, or where experience is limited to one of the alternatives in certain countries.

1 Scope and field of application

This standard classifies decorative laminated sheets (HPL) according to their performance and main recommended fields of application, and provides also for materials of special characteristics, for example postformability or defined reaction to fire.

Requirements are specified for those types of materials that are most generally used, but additional types may be added as required. The limit values specified apply to the most commonly used types of materials, but within each classification, it may be possible to obtain variants having much higher performance figures.

These materials are characterized by their decorative surfaces, which are relatively hard and resistant to wear, scratching, impact, boiling water, domestic stains and moderate heat. They are intended for interior applications as follows:

- Thin single-faced laminates usually less than 2 mm thick, for bonding to a substrate.
- Compact laminates, single or double-faced, approximately 2 mm to 5 mm thick, which need to be rigidly supported without necessarily being bonded to a substrate.
- Compact laminates, self-supporting, double-faced, usually thicker than 5 mm, the thickness of which will be selected according to application and panel dimensions.

The back surface of sheets having only one decorative face is made suitable for adhesive bonding to a substrate.

This standard applies only to decorative laminated sheets as defined in clause 3. The second part of the standard specifies the methods of test.

2 Reference

- EN 438-2 Decorative high-pressure laminates (HPL) - Sheets based on thermosetting resins
Part 2: Determination of properties

3 Definition

For the purposes of this standard the following definition applies.

decorative high-pressure laminated sheet (HPL)

A sheet consisting of layers of fibrous sheet material (for example, paper) impregnated with thermosetting resins and bonded together by means of heat and a pressure of not less than 7 MPa¹⁾, the outer layer or layers on one or both sides having decorative colours or designs.

Decorative high-pressure laminated sheet (HPL) as defined in this standard is made from core layers impregnated with phenolic and/or aminoplastic resins and a surface layer or layers impregnated with aminoplastic resins (mainly melamine resins).

4 Classification

A classification system consists of a material type describing the general characteristics of the laminate together with three index numbers describing levels of performance. This system has been developed to cover the many HPL product variants now available. An alphabetical classification system can be used as an alternative (see 4.5), and table 1 compares the two systems and shows how they relate to some typical applications.

4.1 Index numbers for specifying HPL properties

Index 1 = Resistance to surface wear (table 2).

Index 2 = Resistance to impact by small diameter ball (table 3).

Index 3 = Resistance to scratching (table 4).

4.2 Material type – Special characteristics

The classes of material listed in table 1 are all available as standard type decorative laminated sheet (type S) having the basic characteristics described in clause 1.

For some classes of material, additional types (type P and type F) are also available, possessing the special properties described below.

¹⁾ 1 MPa = 1 MN/m²

Table 1 . Classification system and typical applications

Performance category	Type	Index Number			Equivalent alphabetical classification	Examples of typical applications
		1 Wear	2 Impact	3 Scratch		
Thick materials of high performance for special use in horizontal and vertical applications requiring particularly high impact and moisture resistance	Compact S or Compact F	3	*)	3	CGS (Compact general purpose standard) CGF (Compact general purpose flame retardant)	Doors, partitions, walls, various self-supporting components in construction and transportation
Very high resistance to surface wear High impact resistance Very high resistance to scratching	S or F	4	3	4	HDS (Horizontal heavy duty standard) HDF (Horizontal heavy duty flame retardant)	Countertops, flooring on special substrates
High resistance to surface wear High resistance to impact High resistance to scratching	S, F or P	3	3	3	HGS (Horizontal general purpose standard) HGF (Horizontal general purpose flame retardant) HGP (Horizontal general purpose postforming)	Kitchen working surfaces, restaurant and hotel tables, heavy duty doors and wall coverings, interior walls of public transport vehicles
High resistance to surface wear Moderate resistance to impact High resistance to scratching	S, F or P	3	2	3	-	Horizontal applications for office (computer tables) and bathroom furniture
Moderate resistance to surface wear High resistance to impact Moderate resistance to scratching	S or F	2	3	2	VGS (Vertical general purpose standard) VGF (Vertical general purpose flame retardant)	
Postforming material with moderate resistance to impact	P	2	2	2	VGP (Vertical general purpose postforming)	Front panels for kitchen, office and bathroom furniture, wall coverings, shelves
Low resistance to surface wear Moderate resistance to impact and scratching	S, F or P	1	2	2	-	Special decorative surface effects for vertical use in kitchens, showrooms etc.
Low resistance to surface wear and scratching Moderate resistance to impact	S	1	2	1	VLS (Vertical light duty standard)	Exposed side components of cupboards

*) The test method EN 438-2 no. 11 is not applicable to compact CGS and CGF grades, however in practical applications the impact resistance of compact laminates is superior to that of other decorative laminate types.

4.2.1 Type P – Postformable decorative laminated sheet

Type P sheet is similar to type S, but it can also be formed in accordance with the manufacturer's recommendations.

4.2.2 Type F – Decorative laminated sheet having defined reaction to fire

Type F sheet is similar to type S, but it also meets special requirements of specified fire tests, which may vary according to the application of the material and the country of use.

4.3 Application characteristics

Materials are available in the classes shown in table 1. The list of typical applications given for each category is for guidance only and is not intended to be comprehensive.

Other combinations of properties are possible and can be classified by the numerical index system.

4.4 Index numbers

Index numbers are used to specify three important HPL properties.

4.4.1 Resistance to surface wear (First index number)**Table 2. Index for resistance to surface wear**

Index number	Number of revolutions	
	IP	$\frac{IP + FP}{2}$
1	0	≥ 50
2	≥ 50	≥ 150
3	≥ 150	≥ 350
4	≥ 350	≥ 1000

4.4.2 Resistance to impact by small diameter ball ¹⁾ (Second index number)**Table 3. Index for resistance to impact**

Index number	Spring force (N)
1	≥ 12
2	≥ 15
3	≥ 20
4	≥ 25

¹⁾ Applies only to materials less than 2 mm thick.

²⁾ See annex B.

4.4.3 Resistance to scratching²⁾ (Third index number)**Table 4. Index for resistance to scratching**

Index number	Load (N)
1	≥ 1.5
2	≥ 1.75
3	≥ 2.0
4	≥ 3.0

4.5 Nomenclature

In addition to the prefix HPL and the number of this standard, materials can be specified either by the type and index number system, or by the alphabetical classification system.

For example, horizontal general purpose postforming laminate can be specified as HPL-EN 438 – P333 or HPL-EN 438 – HGP.

5 Requirements**5.1 Compliance**

In order to comply with the requirements of this standard, materials of each type shall meet the requirements of every property for which a value or requirement is specified in clause 6.

Two methods of test are given for the measurement of dimensional stability, impact resistance, resistance to colour change in artificial light, formability and resistance to cigarette burns. When there is a choice of method, material satisfying the requirements of either method shall be deemed to comply with the specification for that property; however, the choice of method may be agreed between the interested parties. The method selected shall be stated in the test report.

5.2 Notes on requirements for reaction to fire

The requirements for reaction to fire are determined by the fire regulations of the country in which the material is to be used.

Actually, it is not possible with a single test, to predict compliance with all the different national requirements. No test is therefore included in this specification and reference must be made to the various requirements when appropriate.

The selection of a suitable test or tests for inclusion in this standard will be considered when International Standards specifying fire tests for building materials and structures have been agreed.

6 Properties

6.1 Colour and pattern

When inspected in daylight or D 65 Standard illuminant and again under a tungsten illuminant, there shall be no significant difference between a standard agreed by the supplier and the specimen under test.

6.2 Surface finish

6.2.1 Finish matching

When inspected at different viewing angles, there shall be no significant difference between a standard agreed by the supplier and the specimen under test.

6.2.2 Reverse side

The reverse side of sheets having only one decorative surface shall be suitable for adhesive bonding if so required.

6.3 Thickness

No requirements for nominal thickness are specified for individual types of material listed in table 7; however, variations from the nominal thickness supplied shall at no point exceed the limits shown in table 5 when thickness is measured in accordance with clause 4 of EN 438-2: 1991.

Table 5. Permitted variations of thickness

Values in millimetres	
Nominal thickness t	Maximum variation
$0.5 \leq t \leq 1.0$	± 0.10
$1.0 < t \leq 2.0$	± 0.15
$2.0 < t \leq 2.5$	± 0.18
$2.5 < t \leq 3.0$	± 0.20
$3.0 < t \leq 4.0$	± 0.25
$4.0 < t \leq 5.0$	± 0.30
$5.0 < t$	as agreed

6.4 Appearance

The following inspection requirements are intended as a general guide, indicating the minimum acceptable quality for laminates supplied as full size sheets. Cut-to-size panels and certain applications involving full size sheets may call for special quality requirements which can be negotiated between supplier and purchaser; in such cases the following requirements may be used as a basis for discussion. It should be noted that only a small percentage of sheets in a batch should be of the minimum acceptable quality.

6.4.1 Surface defects

When inspected according to clause 5 of EN 438-2: 1991, at a distance of 1.5 m, the following surface defects are permissible.

6.4.1.1 Spots, dirt and similar surface defects

The admissible size of defects is based on a maximum contamination area equivalent to $1.0 \text{ mm}^2/\text{m}^2$ laminate and is proportional to the sheet size under inspection.

The total admissible area of contamination may be concentrated in one spot or dispersed over an unlimited amount of smaller defects.

6.4.1.2 Fibres, hairs, scratches

The admissible length of defects is based on a maximum contamination length of $10 \text{ mm}/\text{m}^2$ laminate and is proportional to the sheet size under inspection.

The total admissible length of contamination may be concentrated in one defect or dispersed over an unlimited amount of smaller defects.

6.4.1.3 Combinations of surface defects

When defect types described in 6.4.1.1 and 6.4.1.2 occur in the same sheet, then the maximum level for each of the two types of defect shall not exceed half of the levels prescribed in 6.4.1.1 and 6.4.1.2.

6.4.2 Edge defects

Visual defects (e.g. moisture marks, lack of gloss, etc.) can be present on all four edges of the laminate providing the defect-free length and width are not more than 20 mm shorter than the nominal length and width.

6.4.3 Broken corners

One broken corner of $\leq 3 \text{ cm}$ or two broken corners of $\leq 1.5 \text{ cm}$ are allowed.

These values refer to the distance between the original corner and the fracture line (see figure 1).

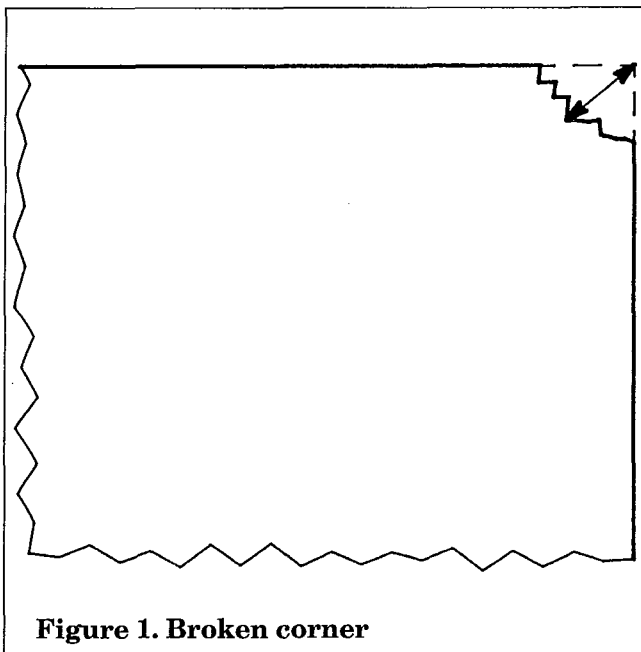


Figure 1. Broken corner

6.4.4 Sanding defects

Slight chatter marks are allowed.

6.4.5 Flatness

The flatness of laminates is dependent on atmospheric conditions within the storage area. Provided that the laminates are stored in the conditions recommended by the manufacturer, they shall not show a departure of the surface from a straightedge of 1 m length in any position, of more than the limits listed in table 6 when the laminate is laid concave side up on a flat surface.

Table 6. Permitted departure from flatness


Values in millimetres		
Composition	Thickness t	Maximum warp
Single-faced laminate	$t < 2.0$	120
	$2.0 \leq t < 5.0$	50
Double-faced laminate	$2.0 \leq t < 5.0$	10
	$5.0 \leq t$	5

6.4.6 Length and width of a full-size laminate


The laminate shall be the nominal size with a tolerance of $_{-0}^{+10}$ mm.

6.4.7 Straightness of edges

The edges shall be straight within a tolerance of 1,5 mm per metre length of the edge (value a in figure 2). The edge being measured shall be at least as long as the 1 m straightedge.

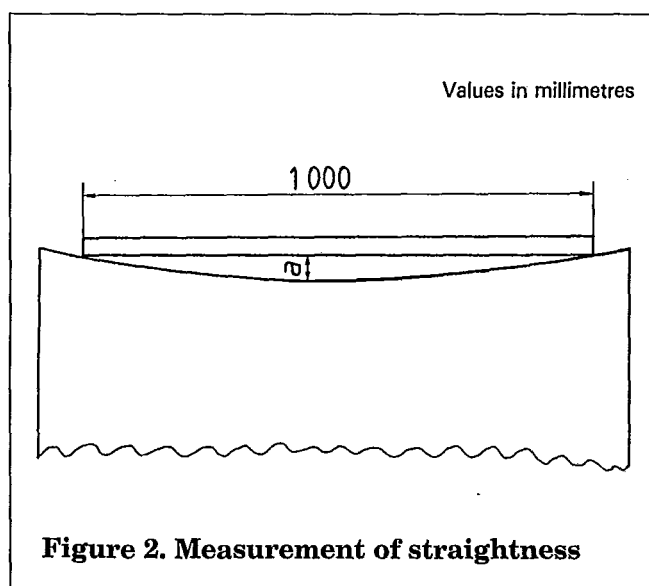**Figure 2. Measurement of straightness****6.4.8 Squareness of the laminate**

The panel shall be rectangular within a tolerance of 1,5 mm per metre length of the edge (value b in figure 3). The edge being measured shall be at least as long as the 1 m straightedge.

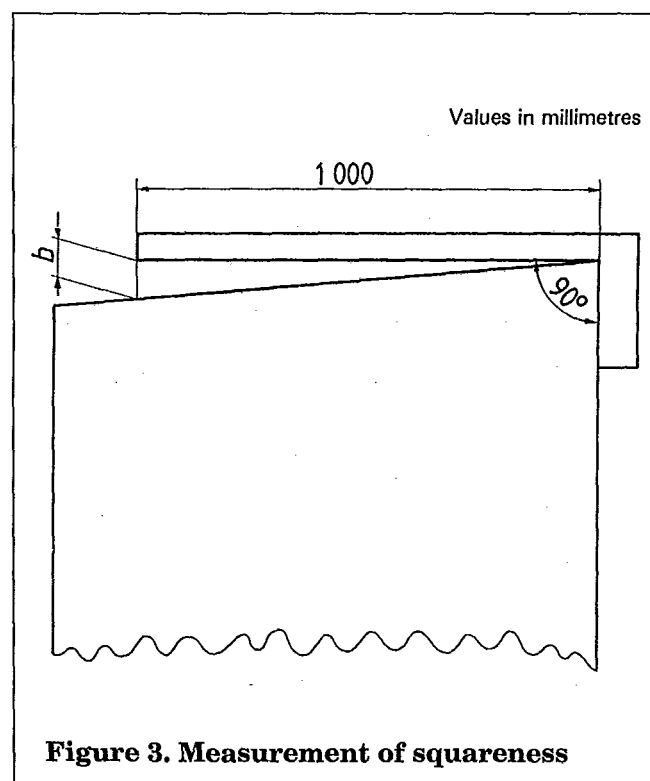**Figure 3. Measurement of squareness****6.5 Other properties**

When tested by the appropriate methods, the properties for each type of material shall satisfy the requirements listed in tables 1 and 7.

Table 7. Property requirements

Property	Test method EN 438-2:1991 Clause no.	Property or attribute	Unit max. or min.	Material type									
				HDS HDF	HGS	HGP	HGF	VGS	VGP	VGF	VLS	CGS	CGF
Resistance to surface wear	6	Wear resistance	revolutions min.	see tables 1 and 2									
Resistance to immersion in boiling water	7	Mass increase Thickness increase Appearance	% max. % max. Grade (not worse than)	see curve 1, annex A									
				4	4	3	4	4	3	4	3	4	4
Resistance to dry heat at 180 °C	8	Appearance gloss others	Grade (not worse than)	3	3	3	3	x	x	x	x	3	3
				4	4	4	4	x	x	x	x	4	4
Dimensional stability at elevated temperature	9 (alternative)	Cumulative dimensional change	% max. (L) % max. (T)	see curve 3, annex A									
Dimensional stability at 20 °C	10 y (alternative)	Cumulative dimensional change	% max. (L) % max. (T)	see curve 4, annex A									
Resistance to impact by small diameter ball	11 u	Spring force	N min.	see tables 1 and 3								a	a
Resistance to impact by large diameter ball (self supporting compact laminates)	12	Drop height Diameter of indentation	cm (min.) mm (max.)	a	a	a	a	a	a	a	a	c	c
				a	a	a	a	a	a	a	a	10	10
Resistance to cracking (thin laminates)	13 u	Appearance	Grade (not worse than)	4	4	4	4	4	4	4	4	a	a
Resistance to scratching	14	Load	See annex B N min.	See tables 1 and 4								e	e
Resistance to staining	15 f	Appearance Groups 1 and 2 Groups 3 and 4	Grade (not worse than)	5	5	5	5	5	5	5	5	5	5
Resistance to colour change in xenon arc light in enclosed carbon arc light	16 (alternative)	Wool standard	min.	6	6	6	6	6	6	6	6	b	b
	17 (alternative)	Wool standard	min.	5	5	5	5	5	5	5	5	b	b
Resistance to cigarette burns	18 (alternative)	Appearance	Grade (not worse than)	3	3	3	3	x	x	x	x	3	3
	19 (alternative)	Time to failure	s min.	110	110	100	100	x	x	x	x	110	100

Table 7. Property requirements (concluded)

Property	Test method EN 438-2: 1991 Clause no.	Property or attribute	Unit max. or min.	Material type									
				HDS HDF	HGS	HGP	HGF	VGS	VGP	VGf	VLS	CGS	CGF
Formability Method A	20 (alternative)	Radius	mm max.	a	a	15z	a	a	10z	a	a	a	a
	21 (alternative)	Radius	mm max.	a	a	15z	a	a	10z	a	a	a	a
Resistance to blistering Method A	22 (alternative)	Time to blister ($t_2 - t_1$)	s min.	a	a	15	a	a	10	a	a	a	a
	23 (alternative)	Time to blister ($t_2 - t_1$)	s min.	a	a	15	a	a	10	a	a	a	a
Resistance to steam	24	Appearance	Grade (not worse than)	4	4	3	4	4	3	4	3	4	4
Resistance to fire	25			x	x	x	q	x	x	q	x	x	q
Resistance to crazing (thick laminate)	26	Susceptibility	Grade (not worse than)	a	a	a	a	a	a	a	a	4	4
Resistance to moisture (Double faced compact laminate)	27	Appearance	Grade (not worse than)	a	a	a	a	a	a	a	a	4	3
Flexural modulus	ISO 178	Stress	MPa min.	a	a	a	a	a	a	a	a	10000	9000
Flexural strength	ISO 178	Stress	MPa min.	a	a	a	a	a	a	a	a	100	80
Tensile strength	ISO/R 527	Stress	MPa min.	a	a	a	a	a	a	a	a	70	60

Key to letters used in table 7.

- a Not applicable.
- b Test sample shall be reduced by machining to a thickness of < 3 mm.
- c Under consideration.
- d Test samples shall be reduced by machining to a thickness of < 15 mm.
- e Test samples shall be reduced by machining to a thickness of < 8 mm.
- f Acids and alkalis in concentrations stronger than those shown in group 3, which can be contained in commercial cleaning agents, can cause surface damage or marking even with very short contact times. Any spillage of such materials must be washed off the laminate surface immediately.
- L In the longitudinal (or machine) direction of the fibrous sheet material (normally the direction of the longest dimension of the laminated sheet).
- q The material shall meet specific requirements for reaction to fire in its application in the country of use.
- T In the cross-longitudinal (or cross-machine) direction of the fibrous sheet material (at right angles to direction L).
- u Applies only to materials less than 2 mm thick.
- x No requirement.
- y Intended to indicate performance under normal climatic conditions.
- z Limits for laminates > 1,5 mm shall be agreed between the interested parties.

Annex A

Addendum to specification table 7, relating to test methods 7, 9 and 10



(This annex forms an integral part of the standard)


In table 7, reference is made to curves 1 to 4 in specifying resistance to boiling water and dimensional stability.

The characteristics are dependent on laminate thickness, and the curves therefore provide more complete information than discrete limits.

The curves give the maximum limiting values for each laminate type (S, P and F). No attempt has been made to prescribe specific laminate thicknesses to the various fields of application, but in determining the quality of a laminate of a given thickness, it is important to know where these properties lie in relation to the appropriate limit curves.


In knowing the expected performance, the customer can select the thickness of laminate which will best meet the requirements of a particular application.

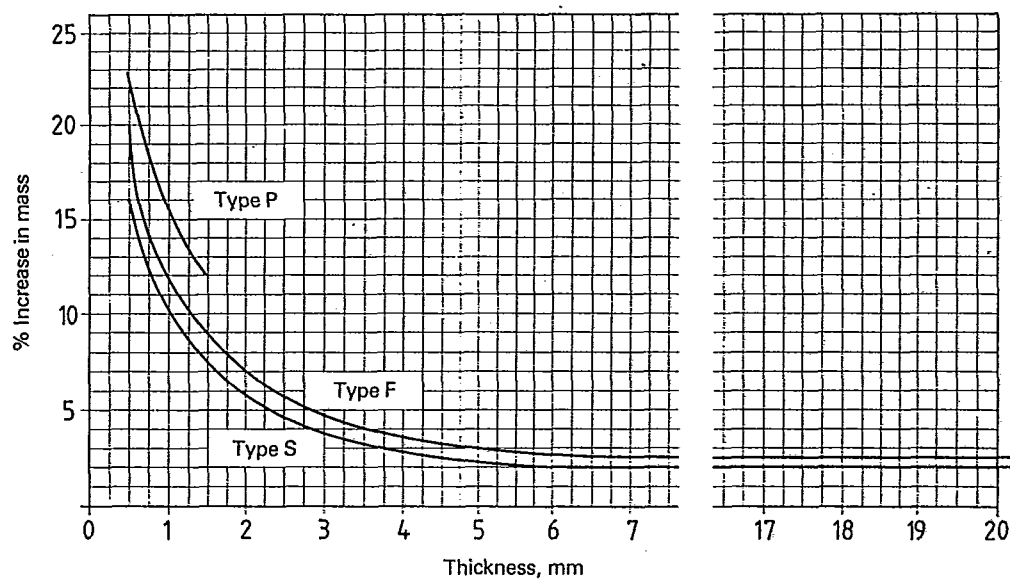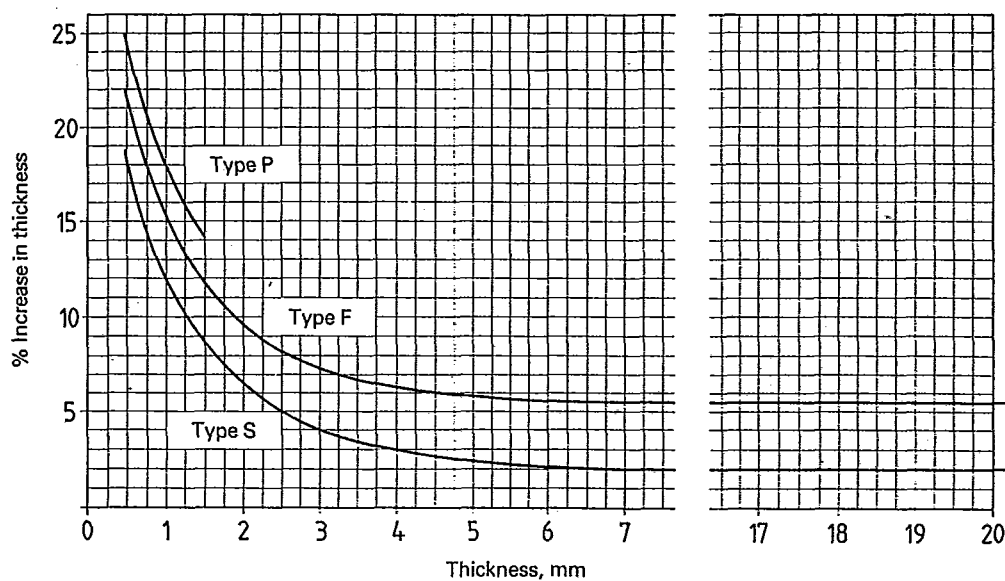**Curve 1. Resistance to immersion in boiling water****Curve 2. Resistance to immersion in boiling water**

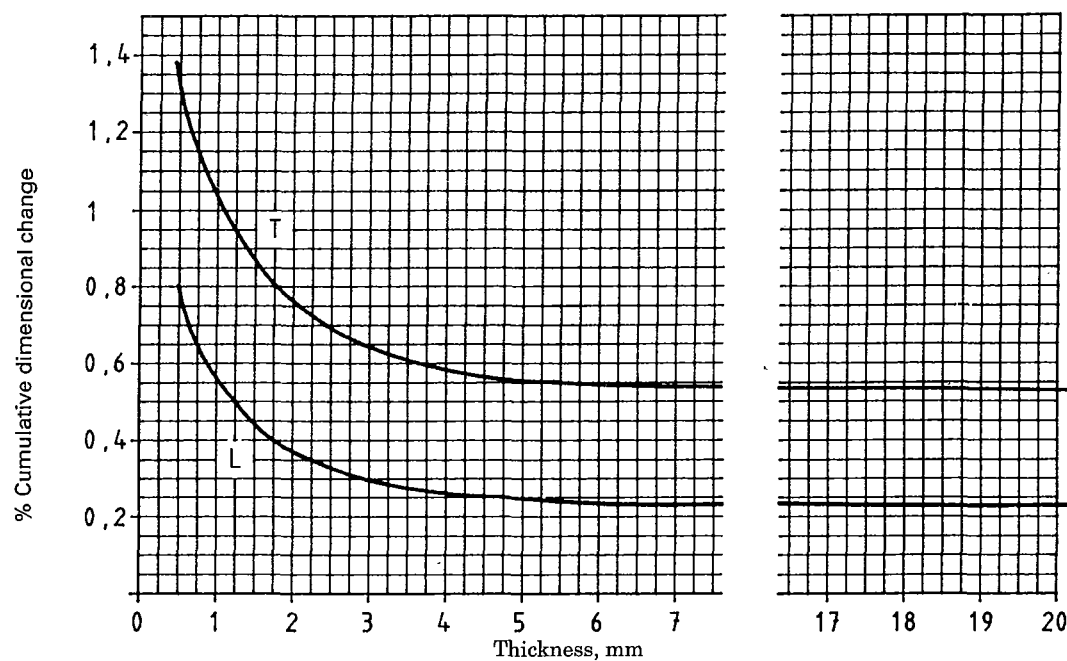

T Cross-longitudinal (or cross-machine) direction
L Longitudinal (or machine) direction

Curve 3. Dimensional stability. Test method 9. Types S, F and P

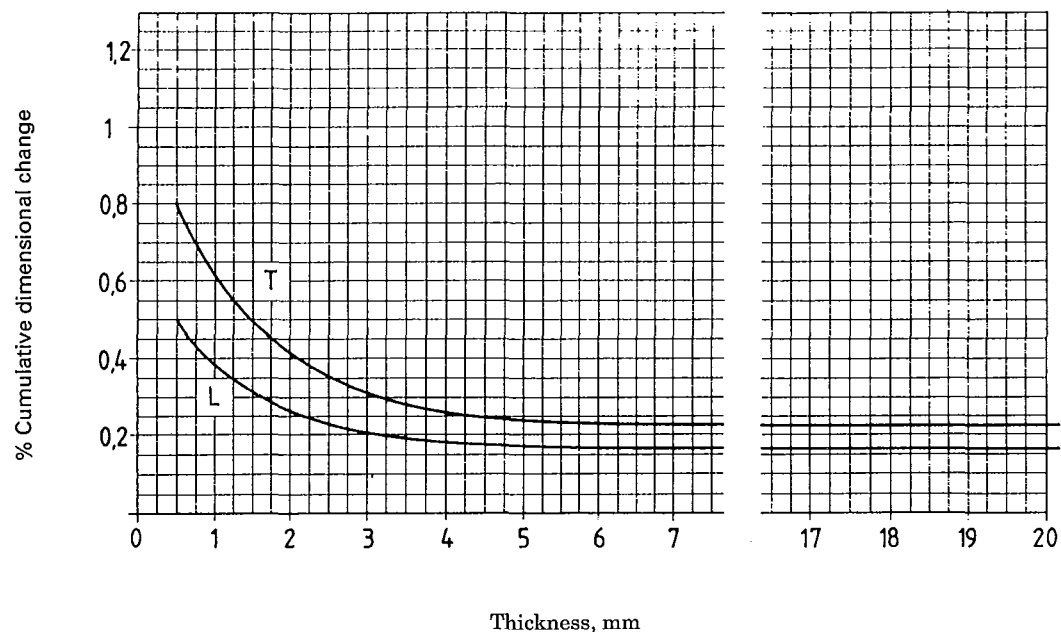

T Cross-longitudinal (or cross-machine) direction
L Longitudinal (or machine) direction

Curve 4. Dimensional stability. Test method 10. Types S, F and P

Annex B

Addendum to specification table 7, relating to test method 14


(This annex forms an integral part of this standard)

The scratch resistance of decorative laminates is influenced by surface finish and colour, and the limits given in table 7 indicate the minimum acceptable performance for each laminate type. However, values which are much higher than these limits can be achieved by selecting particular combinations of colour, print and surface finish.

In general terms, light colours show a better resistance to scratching than dark colours; for a given colour, prints are better than plain colours and textured surface finishes have a better scratch resistance than plain surfaces.

Figure 4 gives an indication of the effect of surface finish and colour on the scratch resistance performance of laminates. The choice of surface finish, colour and print can be made to suit the particular application.

For example: with a deep, rough structure in white, values of about 10 N can be obtained.

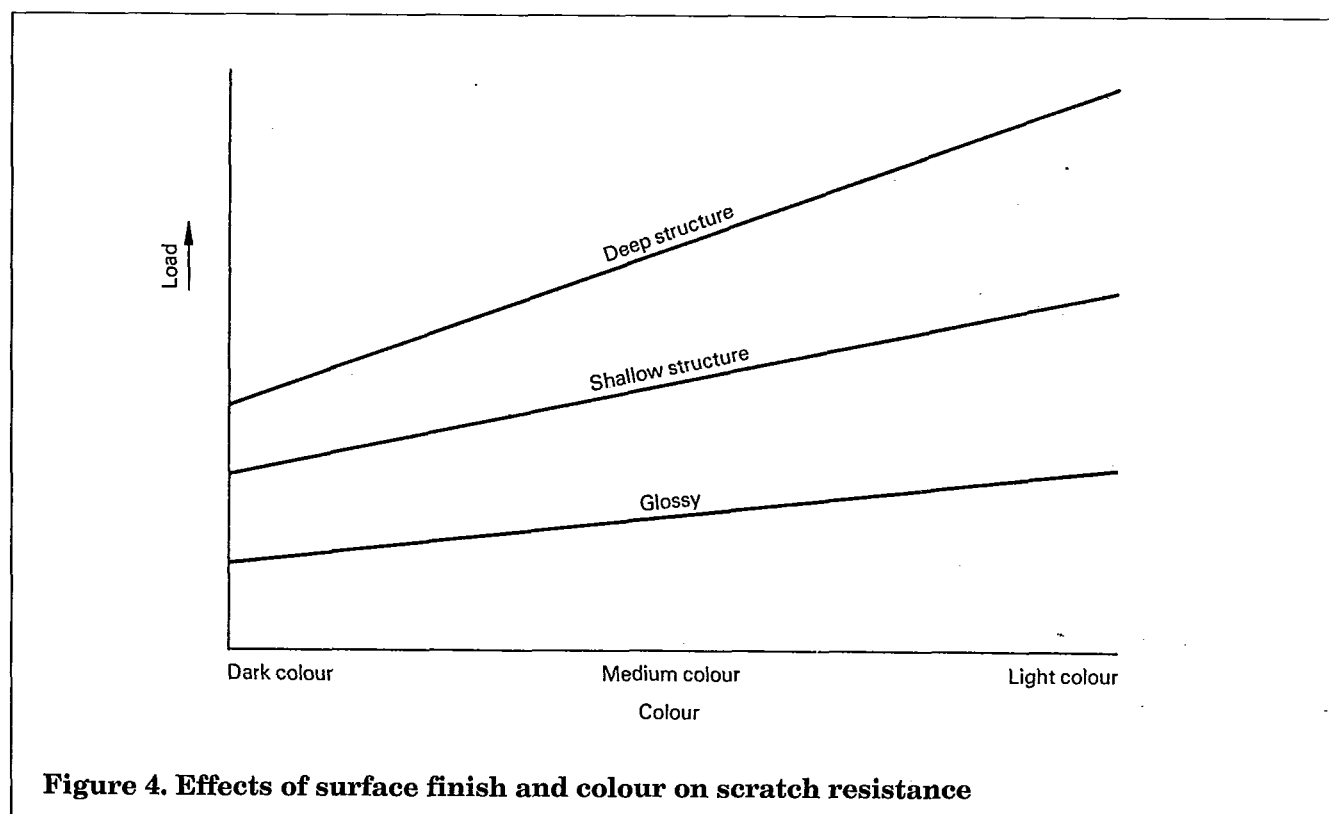

National appendix NA

The United Kingdom participation in the preparation of this European Standard was entrusted by the Plastics and Rubber Standards Policy Committee (PRM/-) to Technical Committee PRM/76 upon which the following bodies were represented:

Association of Suppliers to the Furniture Industry Ltd.
British Laminated Plastics Fabricators Association Ltd.
British Plastics Federation
Fibre Building Board Organisation (FIDOR)
Fibre Cement Manufacturers Association Limited
Furniture Industry Research Association
Standards Association of Australia
United Kingdom and Ireland Particleboard Association

National appendix NB

The British Standard corresponding to the European Standard referred to in the text is identical in number and title with that given in clause 2.

BS EN 438 :
Part 1 : 1991

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Contract requirements

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

Any person who finds an inaccuracy or ambiguity while using this British Standard should notify BSI without delay so that the matter may be investigated swiftly.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying British Standards

Orders for all British Standard publications should be addressed to the Sales Department at Milton Keynes.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library, the Standardline Database, the BSI Information Technology Service (BITS) and its Technical Help to Exporters Service. Contact Customer Information at Milton Keynes: Tel: 0908 221166.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact the Manager, Membership Development at Milton Keynes: Tel: 0908 220022.

Copyright

Copyright subsists in all BSI publications. No part of this publication may be reproduced in any form without the prior permission in writing of BSI. This does not preclude the free use, in the course of implementing the standard, of details such as symbols and size, type or grade designations. Enquiries about copyright should be made to the Copyright Manager, Marketing at Milton Keynes.

BSI
2 Park Street
London
W1A 2BS

BSI
Linford Wood
Milton Keynes
MK14 6LE